

## Observation of anomalous temperature dependence of spectrum on small Fermi surfaces in a BiS<sub>2</sub>-based superconductor

L. K. Zeng,<sup>1</sup> X. B. Wang,<sup>1</sup> J. Ma,<sup>1</sup> P. Richard,<sup>1,2</sup> S. M. Nie,<sup>1</sup> H. M. Weng,<sup>1,2</sup> N. L. Wang,<sup>1,2,3</sup> Z. Wang,<sup>4</sup> T. Qian,<sup>1,\*</sup> and H. Ding<sup>1,2,†</sup>

<sup>1</sup>Beijing National Laboratory for Condensed Matter Physics, and Institute of Physics, Chinese Academy of Sciences, Beijing 100190, China

<sup>2</sup>Collaborative Innovation Center of Quantum Matter, Beijing, China

<sup>3</sup>International Center for Quantum Materials, School of Physics, Peking University, Beijing 100871, China

<sup>4</sup>Department of Physics, Boston College, Chestnut Hill, Massachusetts 02467, USA

(Received 9 February 2014; revised manuscript received 12 July 2014; published 20 August 2014)

We have performed an angle-resolved photoemission spectroscopy study of the BiS<sub>2</sub>-based superconductor Nd(O,F)BiS<sub>2</sub>. Two small electronlike Fermi surfaces around  $X(\pi,0)$  are observed, which enclose 2.4% and 1.1% of the Brillouin zone area, respectively, corresponding to an electron doping of 7% per Bi site. The Fermi surface topology is far from the nesting scenario proposed in most of the theoretical models for the BiS<sub>2</sub>-based superconductors. The conduction bands show significant anisotropic splitting along  $XM$  and  $\Gamma X$ , which is attributed to the cooperative effects of large spin-orbit coupling and interlayer coupling. The low-energy spectrum exhibits a weakly dispersing broad hump near the bottom of the conduction bands. This hump is drastically suppressed with increasing temperature, while the spectral weight at the Fermi level is essentially unaffected. These anomalous spectral features indicate that the electrons could be strongly coupled with the lattice in the low-temperature normal state of this superconductor.

DOI: [10.1103/PhysRevB.90.054512](https://doi.org/10.1103/PhysRevB.90.054512)

PACS number(s): 74.25.Jb, 71.18.+y, 74.25.Kc, 74.70.-b

The recent discovery of superconductivity with  $T_c$  up to  $\sim 10$  K in the BiS<sub>2</sub>-based compounds has attracted a lot of attention [1–11]. As in the cuprate and iron-based high- $T_c$  superconductors, the BiS<sub>2</sub> family has a layered crystal structure consisting of superconducting BiS<sub>2</sub> layers intercalated with various block layers. Band structure calculations show that the parent compound of the BiS<sub>2</sub>-based superconductors is a band insulator with an energy gap of  $\sim 0.8$  eV [12–16], and that bulk superconductivity induced by electron doping is derived from the Bi  $6p_x/p_y$  orbitals, in which correlation effects are expected to be weaker than those in the  $3d$  orbitals of the cuprate and iron-based superconductors. The superconducting transition temperature  $T_c$  reaches a maximum at a nominal doping level  $\delta \sim 0.5$  for many compounds [1–11], where strong nesting between the large parallel Fermi surface (FS) segments is suggested in the band calculations [12–16]. Therefore most of the theoretical models for the pairing mechanism are based on the nesting scenario.

However, there is a large bifurcation regarding the consequences of the nesting. On the one hand, the nesting is proposed to enhance the electron-phonon coupling, thus favoring a conventional BCS superconductivity [12–16]. On the other hand, as widely believed for the iron-based superconductors, the strong FS nesting could enhance charge or spin fluctuations, and thus electronic correlations may play a major role in the superconducting pairing [17–20]. Magnetic penetration depth and muon-spin rotation spectroscopy measurements support a conventional  $s$ -wave superconductivity in the strong electron-phonon coupling limit [21,22], whereas the absence of phonon anomaly in neutron scattering measurements suggests that the electron-phonon coupling may be much weaker than theoret-

ically expected [23]. Recent scanning tunneling spectroscopy measurements show that the ratio  $2\Delta/k_B T_c$  is much larger than the BCS value [24,25]. Giant superconducting fluctuations and an anomalous semiconducting normal state are also observed, suggesting that the superconductivity might be different from that of a conventional BCS superconductor [25].

In this work, we present angle-resolved photoemission spectroscopy (ARPES) results of the BiS<sub>2</sub>-based superconductor Nd(O,F)BiS<sub>2</sub> ( $T_c^{\text{zero}} = 4$  K). Two small electronlike FSs around  $X(\pi,0)$  are observed, corresponding to an electron doping of 7% of itinerant carriers per Bi site. As a result, the measured electronic structure is far from the proposed FS nesting. Furthermore, we reveal that the low-energy spectrum exhibits a broad hump at around  $-0.3$  eV, which is drastically suppressed with increasing temperature, whereas the spectral weight at the Fermi level ( $E_F$ ) is essentially unaffected by the temperature. This exotic spectral behavior suggests that the electrons could be strongly coupled with the lattice in the low-temperature normal state of this superconductor.

Single crystals with a nominal composition of NdO<sub>0.7</sub>F<sub>0.3</sub>BiS<sub>2</sub> were grown by a flux method with KCl/LiCl as the flux. Energy dispersion spectrum (EDS) measurements were performed on several pieces of samples, which give an averaged composition of Nd<sub>0.95±0.02</sub>O<sub>y</sub>F<sub>0.44±0.1</sub>Bi<sub>0.94±0.02</sub>S<sub>2</sub>. From x-ray diffraction measurements, the  $c$  axis is 13.49 Å, which is close to the reported values with the same nominal composition [4,10]. We measured resistivity of several pieces of single crystals from the same batch. The resistivity for all the measured samples reaches zero at  $\sim 4$  K [26]. ARPES measurements were performed at the Institute of Physics, Chinese Academy of Sciences, using the He  $I\alpha$  ( $h\nu = 21.218$  eV) resonance lines. The angular and energy resolutions were set to  $0.2^\circ$  and  $14 \sim 32$  meV, respectively. Samples with a typical size of  $\sim 1 \times 1$  mm<sup>2</sup> were cleaved *in situ* at 30 K and measured between 30 and 230 K in a working vacuum better than

\*tqian@iphy.ac.cn

†dingh@iphy.ac.cn

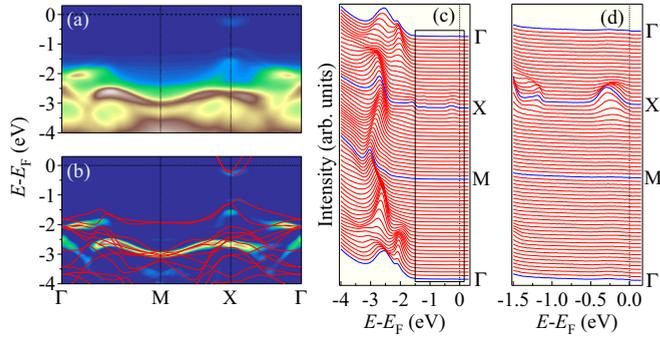


FIG. 1. (Color online) (a) ARPES intensity plot along the high-symmetry lines  $\Gamma$ - $M$ - $X$ - $\Gamma$  taken at 30 K.  $\Gamma$ - $X$  is along the nearest Bi-Bi direction. (b) Corresponding two-dimensional curvature intensity plot. LDA bands without SOC of  $\text{LaO}_{0.5}\text{F}_{0.5}\text{BiS}_2$ , which are essentially the same as those of  $\text{NdO}_{0.5}\text{F}_{0.5}\text{BiS}_2$  in the energy in our experiments [16], are also plotted in (b) for comparison. Calculations were performed using the optimized lattice parameters [13]. The calculated bands are shifted up by 0.5 eV to match the experimental band dispersions. (c) Corresponding EDCs. (d) Magnification of the box in (c).

$4 \times 10^{-11}$  Torr. The  $E_F$  of the samples was referenced to that of a gold film evaporated onto the sample holder.

Figure 1 shows the band dispersions along the high-symmetry lines  $\Gamma$ - $M$ - $X$ - $\Gamma$  in an energy range within 4 eV below  $E_F$ . We observe several dispersive bands below  $-1.2$  eV and an electronlike band dispersion with a bottom of  $-0.3$  eV near  $X$ . There is an energy gap of  $\sim 0.9$  eV between them. To understand the multiband electronic structure, we superimpose the local-density approximation (LDA) band structure on top of our data. The experimental band dispersions are well reproduced by the calculations, especially for the direct gap between the conduction and valence bands and the most prominent band around  $-3$  eV near  $M$ . In LDA calculations, the undoped parent compound is a band insulator and its  $E_F$  is located within the energy gap. The experimentally obtained  $E_F$  is situated in the conduction bands, indicating that electron carriers are introduced in the superconducting samples due to the substitution of O with F.

Figure 2 shows the FS mapping data in the  $k_x$ - $k_y$  plane. We extract two FS pockets centered at  $X$ , which come from the near- $E_F$  electronlike dispersion shown in Fig. 1. The two extracted FSs exhibit a significant anisotropic separation, which is a result of the cooperative effects of spin-orbit coupling (SOC) and interlayer coupling, as explained below. We have performed LDA calculations using the following models. In a one- $\text{BiS}_2$ -layer model (same as the surface layer after cleavage) with SOC [Fig. 2(d)], the near- $E_F$  bands are split along both  $XM$  and  $\Gamma X$  with comparable magnitudes. In a two- $\text{BiS}_2$ -layer model (same as the bulk) without SOC [Fig. 2(e)], the bands are doubly degenerate along  $XM$ , but split along  $\Gamma X$  due to the interlayer coupling. In the presence of SOC, the Rashba term lifts the degeneracy along  $XM$  but the splitting magnitude along  $XM$  is much smaller than along  $\Gamma X$  [Fig. 2(f)], in agreement with our observations.

The two FS pockets enclose 1.1% and 2.4% of the Brillouin zone area, respectively. Counting the Luttinger volume of

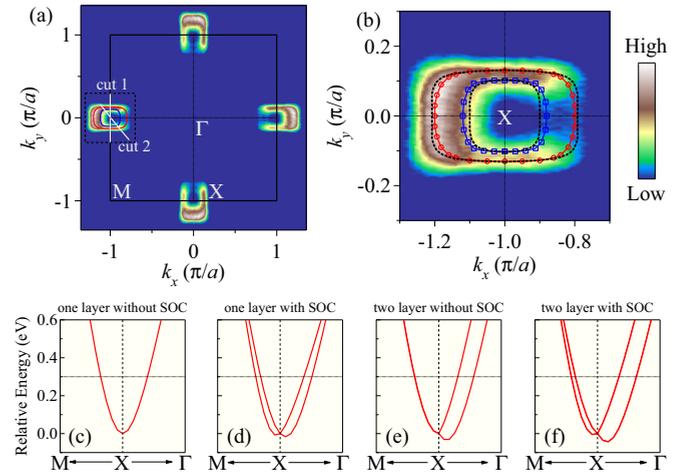


FIG. 2. (Color online) (a) ARPES intensity plot at  $E_F$  as a function of the two-dimensional wave vector taken at 30 K. The intensity is obtained by integrating the spectra within  $\pm 15$  meV with respect to  $E_F$ . The data are symmetrized by assuming a fourfold symmetry with respect to  $\Gamma$ . Red and blue lines represent the extracted FSs. White lines labeled cut 1 and cut 2 indicate the momentum locations, along which the data are shown in Figs. 3 and 4, respectively. (b) Magnification of the dashed box in (a). Circles and squares show the experimentally determined  $k_F$  points. Dashed black lines represent the LDA+SOC calculated FSs. (c, d) Calculated conduction bands at  $X$  using one- $\text{BiS}_2$ -layer models with and without SOC, respectively. (e, f) Same as (c) and (d), respectively, but using two- $\text{BiS}_2$ -layer models. In (c)–(f), the zero energy is defined to the band bottom at  $X$  and the horizontal dashed lines at 0.3 eV represent the approximate position of  $E_F$ .

two-dimensional FS sheets, the two observed FSs correspond to an electron doping of 7% per Bi site. This value for doped itinerant carrier density is much less than those inferred from the nominal composition and the EDS data. The discrepancy can be explained in several ways. First, the possibility of charge polarization at the terminal layer cannot be completely excluded, though this scenario is unlikely since the cleavage occurs between two symmetrical  $\text{BiS}_2$  layers. Moreover, the plasma frequency calculated using the experimental doping level is  $\sim 2.1$  eV, in agreement with the optical data [26], suggesting that the ARPES data reflect the intrinsic carrier density in the bulk. Second, as both oxygen and fluorine are light elements, their concentrations given from the EDS data may not be reliable [25]. Third, part of the carriers may be localized and thus do not contribute to the conduction band. In this case, the localized carriers could form flatbands within the energy gap.

Figure 3 shows ARPES data of the conduction bands taken along  $XM$  at 30 K. By tracking the peak positions of the momentum distribution curves (MDCs), we extract two electronlike bands, as shown in Figs. 3(b) and 3(d). The band dispersion follows the LDA bands calculated with SOC well. As mentioned above, the band splitting along  $XM$  originates from the SOC. On the other hand, the energy distribution curves (EDCs) are characterized by a broad hump, whose maximum does not cross  $E_F$  but tends to bend back beyond  $k_{F2}$  [Fig. 3(c)]. As shown in Fig. 3(e), the EDC at  $k_{F2}$  shows

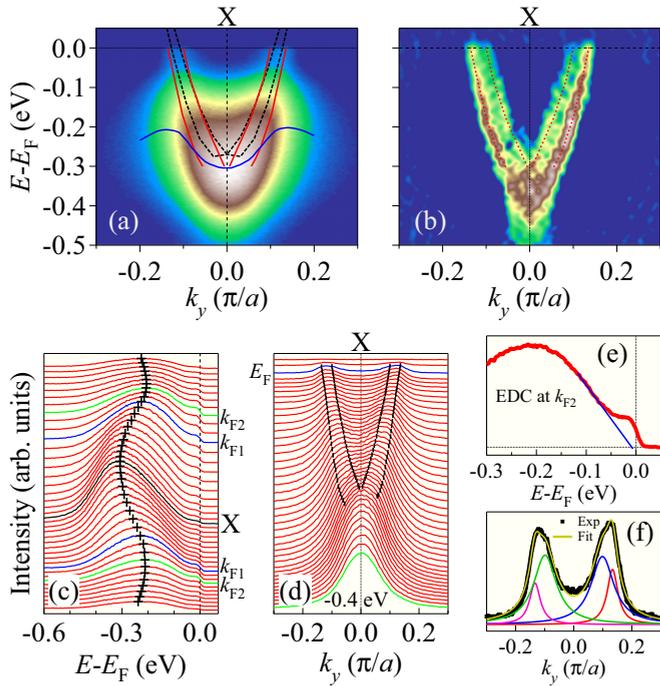


FIG. 3. (Color online) (a) ARPES intensity plot along  $XM$  [cut 1 from Fig. 2(a)] taken at 30 K. Red and blue lines represent the dispersions extracted from the peak positions of the MDCs and EDCs, respectively. Dashed black lines represent the LDA+SOC calculated bands. (b) Corresponding intensity plot of second derivative along momentum. Dotted lines are the same as the red lines in (a). (c) Corresponding EDCs. Crosses indicate the peak positions of the EDCs. Black, blue, and green curves represent the EDCs at  $X$ ,  $k_{F1}$ , and  $k_{F2}$ , respectively.  $k_{F1}$  and  $k_{F2}$  are the Fermi wave vectors of the inner and outer electronlike bands, respectively. (d) Corresponding MDCs. Short verticals indicate the peak positions of the MDCs. Blue and green curves represent the MDCs at  $E_F$  and  $-0.4$  eV, respectively. (e) EDC at  $k_{F2}$ . Blue line represents a linear extrapolation of the slope on the lower-binding-energy side of the hump. (f) MDC at  $E_F$ . The MDC is fitted to four Lorentzian peaks, indicating the band splitting along  $XM$  due to SOC.

a sharp Fermi cutoff, indicating a metallic behavior. There is a change of the slope on the lower binding energy side of the hump at  $\sim -0.05$  eV. The linear extrapolation suggests that the hump contributes vanishingly small spectral weight at  $E_F$ , indicating that the finite low-energy spectral weight at  $E_F$  is dominated by another branch, which will be discussed later.

The low-energy spectrum shows anomalous temperature dependence characterized by a rapid suppression of the spectral weight of the broad hump with increasing temperature that, nevertheless, leaves the near- $E_F$  spectral weight little changed. The temperature-dependent ARPES results along cut 2 are shown in Fig. 4. A sharp contrast between the intensity contours at 30 K [Fig. 4(a)] and 230 K [Fig. 4(b)] is clearly visible. To further clarify the evolution of the spectrum with temperature, we plot the MDCs at  $E_F$  and the EDCs at  $k_F$  of the left branch at various temperatures between 30 and 230 K in Figs. 4(d) and 4(e), respectively. All the spectra are normalized by the photon flux. To remove the thermal broadening effect due to the Fermi-Dirac statistics, the

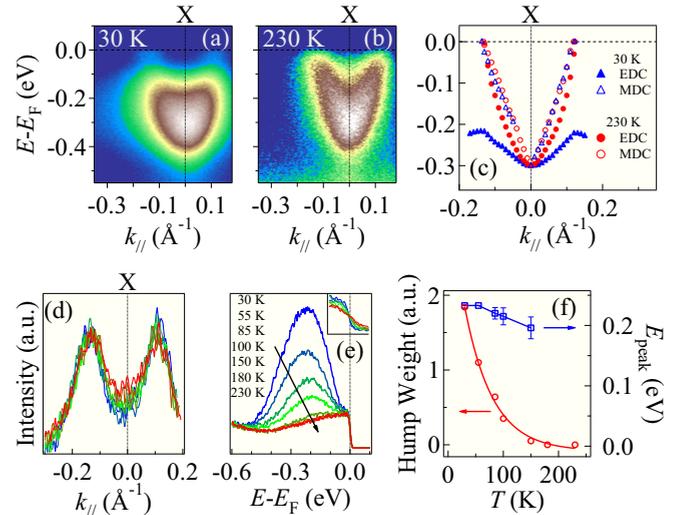


FIG. 4. (Color online) (a, b) ARPES intensity plots through the  $X$  point [cut 2 from Fig. 2(a)] taken at 30 and 230 K, respectively. (c)  $E$ - $k$  plot of the positions of the EDC and MDC peaks taken at 30 and 230 K, respectively. To approximately remove the effect of the Fermi function to the EDC peak position near  $E_F$ , the EDC peak position is extracted from the symmetrized curve with respect to  $E_F$ . (d, e) MDCs at  $E_F$  and EDCs at  $k_F$  of the left branch taken at various temperatures between 30 and 230 K, respectively. The thermal broadening effect on the EDCs in (e) is removed (see text for details). Inset of (e) plots the EDCs (raw data) in an energy window of  $[-0.05, 0.05]$  eV. (f) Spectral weight (left axis) and binding energy of the maximum (right axis) of the broad hump against temperature. The spectral weight is obtained by subtracting the integration of the EDC at 230 K from that taken at the corresponding temperature.

EDCs in Fig. 4(e) are divided by resolution-convoluted Fermi functions at corresponding temperatures and then multiplied by 10 K. The MDCs almost collapse onto a single curve, whereas the line shape of the EDCs changes drastically with temperature. The spectral weight of the broad hump is suppressed rapidly with increasing temperature. The hump can no longer be clearly resolved above 150 K and the spectra at 180 and 230 K nearly coincide. In sharp contrast to the loss of spectral weight below  $E_F$ , the Fermi cutoff of all the EDCs (raw data) taken at various temperatures crosses exactly at  $E_F$  [inset of Fig. 4(e)], which is consistent with the collapse of the MDCs shown in Fig. 4(d), indicating a negligible temperature effect on the spectral weight at  $E_F$ . As shown in Fig. 4(c), with the suppression of the broad hump, the dichotomy between the dispersions of EDC and MDC peaks is almost eliminated at 230 K. The dispersion at 230 K is consistent with the one extracted from the MDCs at 30 K. This suggests that the MDC peaks at 30 K track the bare band dispersion, which is essentially unaffected with temperature.

A conventional explanation for temperature-induced loss of spectral weight is through the effect of lattice vibrations. Such an effect in photoemission spectra is similar to that found in x-ray and neutron scattering, where the intensities of diffraction peaks are multiplied by the Debye-Waller factor  $e^{-2W}$  ( $W \propto T$ ) [27]. Indeed, the integrated spectral weight as a function of temperature can be approximately fitted to a function of  $A + Be^{-CT}$ , as shown in Fig. 4(f). However, the extracted Debye

temperature from the fitting is about only 3 K [28], 2 orders of magnitudes smaller than the estimated values from the specific heat data [6,7,29–31]. Therefore the effect of conventional lattice vibrations cannot explain the giant temperature effects in our data.

Loss of spectral weight in a large energy scale has been observed in a polaronic state of the colossal magnetoresistant manganites  $\text{La}_{2-2x}\text{Sr}_{1+2x}\text{Mn}_2\text{O}_7$  [32–35]. In the polaronic state induced by strong electron-phonon coupling, the spectral function consists of a low-energy “zero-phonon” quasiparticle peak and a hump-like high-energy incoherent resonance. Our observation of a high-energy hump as well as a sharp Fermi cutoff bears some resemblance to the signature of polarons. In the polaronic state of the manganites, the MDC peaks track the bare band dispersion [36], which also seems to be in agreement with our results. In the manganites, the incoherent branch loses its partial spectral weight over an energy range of up to 0.8 eV, which is accompanied by a disappearance of the quasiparticle peaks around the metal-insulator transition temperature. This could be associated with either loss of polaron coherence [34] or a decreased fraction of metallic regions in the scenario of phase separation [33]. Assuming that the polaronic picture could be applied to the  $\text{BiS}_2$  system, the spectral weight of the incoherent branch, i.e., the broad hump, is drastically suppressed with increasing temperature, while the low-energy coherent branch, which dominates the spectral weight at  $E_F$ , is not affected. The behavior looks very unusual in the framework of polarons because the strong suppression of the incoherent branch indicates significant changes of the polaronic states, which seems not to be perceived by the coherent part. Our spectra exhibit a distinctly different temperature dependence from that in the manganites, indicating that the giant thermal effects observed in the two systems might have different origins.

The disorder-induced self-trapping of polarons in  $\text{Na}_{0.025}\text{WO}_3$  also shows nontrivial temperature dependence of the spectral function [37,38]. The  $\text{Na}_x\text{WO}_3$  and  $\text{BiS}_2$  systems bear an interesting resemblance in their electronic structures. Their undoped parent compounds are band insulators with energy gaps of an order of electronvolts between the valence

and conduction bands. The introduction of electron carriers by element substitutions or intercalations leads to an insulator-metal transition on small electronlike FSs. The conduction electrons in  $\text{Na}_{0.025}\text{WO}_3$  are self-trapped due to strong disorder induced by the randomly distributed  $\text{Na}^+$  ions, forming a weakly dispersive polaron band near the top of valence bands. The breakdown of polarons at high temperature leads to a large decrease in the intensity of the polaron band, while the spectrum of the conduction band is not significantly changed. These properties are quite similar to what we have observed in  $\text{BiS}_2$ , except that the polaron band would be localized near the bottom of the conduction bands in our case. We note that the polaronic self-trapping of carriers could also explain the small FS pockets observed in our experiment. It is expected that as the polarons become more delocalized, the spectral weight should be transferred to other  $k$  points. However, such a spectral weight transfer is not observed, at least along the measured momentum cut. Since the sum rule needs to be obeyed, it is possible that the spectral weight is transferred to other energy and/or momentum regions beyond the measurement range.

In summary, our ARPES results show two small electronlike FSs around  $X(\pi,0)$  instead of large holelike FSs centered at  $\Gamma(0,0)$  and  $M(\pi,\pi)$ , as proposed in recent theoretical models. The anomalous temperature dependence of the low-energy spectrum indicates that the electrons could be strongly coupled with the lattice in the low-temperature normal state of this superconductor. Our results provide detailed information on the low-energy electronic states and valuable insights for further experimental and theoretical studies of the pairing mechanism in  $\text{BiS}_2$ -based superconductors.

We acknowledge X. Dai and Z. Fang for valuable discussions. This work was supported by grants from CAS (2010Y1JB6 and XDB07000000), MOST (2010CB923000, 2011CBA001000, 2011CB921701, 2013CB921700, 2011CBA00108, and 2012CB821403), NSFC (11004232, 11050110422, 11274362, 11234014, 11120101003, 11074291, 11274359, and 11104339), and DOE (DE-FG02-99ER45747 and DE-SC0002554).

- 
- [1] Y. Mizuguchi, H. Fujihisa, Y. Gotoh, K. Suzuki, H. Usui, K. Kuroki, S. Demura, Y. Takano, H. Izawa, and O. Miura, *Phys. Rev. B* **86**, 220510(R) (2012).
- [2] S. K. Singh, A. Kumar, B. Gahtori, Shruti, G. Sharma, S. Patnaik, and V. P. S. Awana, *J. Am. Chem. Soc.* **134**, 16504 (2012).
- [3] Y. Mizuguchi, S. Demura, K. Deguchi, Y. Takano, H. Fujihisa, Y. Gotoh, H. Izawa, and O. Miura, *J. Phys. Soc. Jpn.* **81**, 114725 (2012).
- [4] S. Demura, Y. Mizuguchi, K. Deguchi, H. Okazaki, H. Hara, T. Watanabe, S. J. Denholme, M. Fujioka, T. Ozaki, H. Fujihisa, Y. Gotoh, O. Miura, T. Yamaguchi, H. Takeya, and Y. Takano, *J. Phys. Soc. Jpn.* **82**, 033708 (2013).
- [5] J. Xing, S. Li, X. Ding, H. Yang, and H. H. Wen, *Phys. Rev. B* **86**, 214518 (2012).
- [6] X. Lin, X. X. Ni, B. Chen, X. F. Xu, X. X. Yang, J. H. Dai, Y. K. Li, X. J. Yang, Y. K. Luo, Q. Tao, G. H. Cao, and Z. A. Xu, *Phys. Rev. B* **87**, 020504(R) (2013).
- [7] D. Yazici, K. Huang, B. D. White, I. Jeon, V. W. Burnett, A. J. Friedman, I. K. Lum, M. Nallaiyan, S. Spagna, and M. B. Maple, *Phys. Rev. B* **87**, 174512 (2013).
- [8] K. Deguchi, Y. Mizuguchi, S. Demura, H. Hara, T. Watanabe, S. J. Denholme, M. Fujioka, H. Okazaki, T. Ozaki, H. Takeya, T. Yamaguchi, O. Miura, and Y. Takano, *Europhys. Lett.* **101**, 17004 (2013).
- [9] S. Demura, K. Deguchi, Y. Mizuguchi, K. Sato, R. Honjyo, A. Yamashita, T. Yamaki, H. Hara, T. Watanabe, S. J. Denholme, M. Fujioka, H. Okazaki, T. Ozaki, O. Miura, T. Yamaguchi, H. Takeya, and Y. Takano, [arXiv:1311.4267](https://arxiv.org/abs/1311.4267).
- [10] R. Jha and V. P. S. Awana, *Mat. Res. Express* **1**, 016002 (2014).

- [11] R. Jha, B. Tiwari, and V. P. S. Awana, *J. Phys. Soc. Jpn.* **83**, 063707 (2014).
- [12] H. Usui, K. Suzuki, and K. Kuroki, *Phys. Rev. B* **86**, 220501(R) (2012).
- [13] X. G. Wan, H. C. Ding, S. Y. Savrasov, and C. G. Duan, *Phys. Rev. B* **87**, 115124 (2013).
- [14] B. Li, Z. W. Xing, and G. Q. Huang, *Europhys. Lett.* **101**, 47002 (2013).
- [15] T. Yildirim, *Phys. Rev. B* **87**, 020506(R) (2013).
- [16] C. Morice, E. Artacho, S. E. Dutton, D. Molnar, H. J. Kim, and S. S. Saxena, [arXiv:1312.2615](https://arxiv.org/abs/1312.2615).
- [17] T. Zhou and Z. D. Wang, *J. Supercond. Novel Magn.* **26**, 2735 (2013).
- [18] G. B. Martins, A. Moreo, and E. Dagotto, *Phys. Rev. B* **87**, 081102(R) (2013).
- [19] Y. Yang, W. S. Wang, Y. Y. Xiang, Z. Z. Li, and Q. H. Wang, *Phys. Rev. B* **88**, 094519 (2013).
- [20] Y. Liang, X. X. Wu, W. F. Tsai, and J. P. Hu, *Front. Phys.* **9**, 194 (2014).
- [21] G. Lamura, T. Shiroka, P. Bonfa, S. Sanna, R. De Renzi, C. Baines, H. Luetkens, J. Kajitani, Y. Mizuguchi, O. Miura, K. Deguchi, S. Demura, Y. Takano, and M. Putti, *Phys. Rev. B* **88**, 180509(R) (2013).
- [22] Shruti, P. Srivastava, and S. Patnaik, *J. Phys.: Condens. Matter* **25**, 339601 (2013).
- [23] J. Lee, M. B. Stone, A. Huq, T. Yildirim, G. Ehlers, Y. Mizuguchi, O. Miura, Y. Takano, K. Deguchi, S. Demura, and S. H. Lee, *Phys. Rev. B* **87**, 205134 (2013).
- [24] S. Li, H. Yang, D. Fang, Z. Wang, J. Tao, X. Ding, and H. H. Wen, *Sci. China-Phys. Mech. Astron.* **56**, 2019 (2013).
- [25] J. Z. Liu, D. L. Fang, Z. Y. Wang, J. Xing, Z. Y. Du, X. Y. Zhu, H. Yang, and H. H. Wen, [arXiv:1310.0377](https://arxiv.org/abs/1310.0377).
- [26] X. B. Wang, S. M. Nie, H. P. Wang, P. Zheng, P. Wang, T. Dong, H. M. Weng, and N. L. Wang, *Phys. Rev. B* **90**, 054507 (2014).
- [27] S. Hüfner, *Photoelectron Spectroscopy: Principles and Application* (Springer-Verlag, New York, 1995).
- [28] In the calculation,  $\Delta k$  is defined to be  $(0, 0, 2\pi/c)$ .
- [29] H. Takatsu, Y. Mizuguchi, H. Izawa, O. Miura, and H. Kadowaki, *J. Phys. Soc. Jpn.* **81**, 125002 (2012).
- [30] R. Jha, A. Kumar, S. K. Singh, and V. P. S. Awana, *J. Appl. Phys.* **113**, 056102 (2013).
- [31] D. Yazici, K. Huang, B. D. White, A. H. Chang, A. J. Friedman, and M. B. Maple, *Philos. Mag.* **93**, 673 (2013).
- [32] S. de Jong, Y. Huang, I. Santoso, F. Massee, R. Follath, O. Schwarzkopf, L. Patthey, M. Shi, and M. S. Golden, *Phys. Rev. B* **76**, 235117 (2007).
- [33] Z. Sun, J. F. Douglas, A. V. Fedorov, Y. D. Chuang, H. Zheng, J. F. Mitchell, and D. S. Dessau, *Nat. Phys.* **3**, 248 (2007).
- [34] N. Mannella, W. L. Yang, X. J. Zhou, H. Zheng, J. F. Mitchell, J. Zaanen, T. P. Devereaux, N. Nagaosa, Z. Hussain, and Z. X. Shen, *Nature (London)* **438**, 474 (2005).
- [35] N. Mannella, W. L. Yang, K. Tanaka, X. J. Zhou, H. Zheng, J. F. Mitchell, J. Zaanen, T. P. Devereaux, N. Nagaosa, Z. Hussain, and Z. X. Shen, *Phys. Rev. B* **76**, 233102 (2007).
- [36] Z. Sun, Y. D. Chuang, A. V. Fedorov, J. F. Douglas, D. Reznik, F. Weber, N. Aliouane, D. N. Argyriou, H. Zheng, J. F. Mitchell, T. Kimura, Y. Tokura, A. Revcolevschi, and D. S. Dessau, *Phys. Rev. Lett.* **97**, 056401 (2006).
- [37] S. Raj, D. Hashimoto, H. Matsui, S. Souma, T. Sato, T. Takahashi, D. D. Sarma, P. Mahadevan, and S. Oishi, *Phys. Rev. Lett.* **96**, 147603 (2006).
- [38] S. Raj, T. Sato, S. Souma, and T. Takahashi, *Mod. Phys. Lett. B* **23**, 2819 (2009).