

PAPER

## Surface State Bands in Superconducting $(\text{Pt}_x\text{Ir}_{1-x})\text{Te}_2$

To cite this article: Kong Wan-Dong *et al* 2015 *Chinese Phys. Lett.* **32** 077402

View the [article online](#) for updates and enhancements.

Surface State Bands in Superconducting  $(\text{Pt}_x\text{Ir}_{1-x})\text{Te}_2$  \*

KONG Wan-Dong(孔万东)<sup>1</sup>, MIAO Hu(苗虎)<sup>1</sup>, QIAN Tian(钱天)<sup>1\*\*</sup>, WANG Zhi-Jun(王志俊)<sup>1</sup>,  
 XU Gang(徐刚)<sup>1</sup>, FANG Ai-Fang(房爱芳)<sup>1</sup>, HUANG Yao-Bo(黄耀波)<sup>1</sup>, ZHANG Peng(张鹏)<sup>1</sup>,  
 SHI Xun(施训)<sup>1</sup>, FANG Zhong(方忠)<sup>1,2</sup>, DAI Xi(戴希)<sup>1,2</sup>, RICHARD Pierre(芮夏岩)<sup>1,2</sup>,  
 WANG Nan-Lin(王楠林)<sup>1,2,3</sup>, DING Hong(丁洪)<sup>1,2\*\*</sup>

<sup>1</sup>Beijing National Laboratory for Condensed Matter Physics, Institute of Physics,  
 Chinese Academy of Sciences, Beijing 100190

<sup>2</sup>Collaborative Innovation Center of Quantum Matter, Beijing 100871

<sup>3</sup>International Center for Quantum Materials, School of Physics, Peking University, Beijing 100871

(Received 16 March 2015)

Angle-resolved photoemission spectroscopy is performed to study the bulk and surface electronic structures of non-superconducting  $\text{IrTe}_2$  and superconducting  $\text{Pt}_{0.05}\text{Ir}_{0.95}\text{Te}_2$ . In addition to the bulk electronic bands predicted by the local density approximation calculations, we observe two Dirac cone-like bands at the Brillouin zone center, which are non-dispersive along  $k_z$ , suggesting that the extra bands are surface state bands. As the experimental results are well consistent with the *ab initio* calculations of surface states, the parity analysis proves that these surface state bands are topologically trivial and thus exclude  $(\text{Pt}_x\text{Ir}_{1-x})\text{Te}_2$  as a possible topological superconductor candidate.

PACS: 74.25.Jb, 74.70.Xa, 74.20.Mn


DOI: 10.1088/0256-307X/32/7/077402

Topological superconductivity is a new state of matter, which is expected to exhibit massless Majorana fermions and to provide a route for topological quantum computation.<sup>[1–5]</sup> While the realization of topological superconductors (TSCs) is highly demanded, the only serious TSC candidates are arguably the time-reversal breaking p-wave superconductor  $\text{Sr}_2\text{RuO}_4$  and the chemically-substituted topological insulators.<sup>[6–16]</sup>

Very recently, the strong spin-orbit coupling (SOC) material  $\text{IrTe}_2$  has attracted wide interest due to the emergence of superconductivity and the possible realization of a TSC in Pt-doped  $(\text{Pt}_x\text{Ir}_{1-x})\text{Te}_2$ .<sup>[17–21]</sup>  $\text{IrTe}_2$  is a layered compound with 1T-structure at room temperature, where the Ir and Te atoms form regular triangle lattices in their respective (001) planes, as illustrated in Fig. 1(a). It exhibits a structural phase transition at  $T_s = 265$  K, below which a new structural modulation with a wave vector  $Q = (1/5, 0, -1/5)$  was revealed.<sup>[17]</sup> Substitution of Ir by Pt or Pd suppresses the structural phase transition and eventually induces bulk superconductivity.<sup>[17–21]</sup>

To justify whether the topological superconductivity can be realized in the 5d transition metal compound  $(\text{Pt}_x\text{Ir}_{1-x})\text{Te}_2$ , we have performed angle-resolved photoemission spectroscopy (ARPES) studies on both the bulk and surface electronic structures of non-superconducting  $\text{IrTe}_2$  and superconducting  $\text{Pt}_{0.05}\text{Ir}_{0.95}\text{Te}_2$ . While two Dirac cone-like bands

at the Brillouin center are identified as surface state bands (SSBs), our local density approximation (LDA) calculations and parity analysis prove that these SSBs are topologically trivial and exclude  $(\text{Pt}_x\text{Ir}_{1-x})\text{Te}_2$  as a possible TSC candidate.

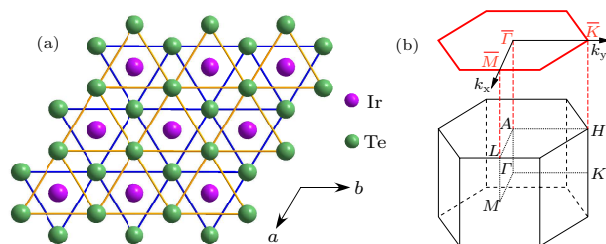

**Fig. 1.** (Color online) (a) Top view of an  $\text{IrTe}_2$  layer. Blue and yellow lines represent Te-Te bonds within the Te layers above and below the Ir layer, respectively. (b) Hexagonal 3D Brillouin zone of  $(\text{Pt}_x\text{Ir}_{1-x})\text{Te}_2$  with the definitions of high-symmetry points.

Single crystals of  $(\text{Pt}_x\text{Ir}_{1-x})\text{Te}_2$  have been grown via the self-flux technique.<sup>[18]</sup> Mixtures of Ir(Pt) powder and Te pieces in an atomic ratio of 0.18:0.82 were placed in an  $\text{Al}_2\text{O}_3$  crucible and were sealed in an evacuated quartz tube. The mixtures were initially heated up and kept at  $950^\circ\text{C}$  for several hours, then at  $1160^\circ\text{C}$  for one day, and finally cooled down slowly to  $900^\circ\text{C}$  at a rate of  $2^\circ\text{C}/\text{h}$ . The Te flux was separated from single crystals by using a centrifuge. ARPES experiments were performed at beamlines PGM and Apple-PGM of the synchrotron radiation center (Wis-

\*Supported by the National Basic Research Program of China under Grant No 2013CB921700, the Strategic Priority Research Program of Chinese Academy of Sciences under Grant No XDB07000000, and the National Natural Science Foundation of China under Grant Nos 11204359 and 11121063.


\*\*Corresponding author. Email: tqian@iphy.ac.cn; dingh@iphy.ac.cn

© 2015 Chinese Physical Society and IOP Publishing Ltd

consin) equipped with a Scienta R4000 analyser and a Scienta SES 200 analyser, respectively. The energy and angular resolutions were set at 30 meV and  $0.2^\circ$ , respectively. The samples were cleaved *in situ* and measured in a vacuum better than  $3 \times 10^{-11}$  Torr.

We first focus on the electronic structure of the pristine material IrTe<sub>2</sub>. In Fig. 2, we show the ARPES curvature intensity plots<sup>[22]</sup> of IrTe<sub>2</sub> along the  $K$ - $\Gamma$ - $M$  direction at different photon energies of IrTe<sub>2</sub>. The LDA+SOC band structures along the high-symmetry path at  $k_z = \pi$  and 0 are also plotted in Figs. 2(b) and 2(c), respectively. We find qualitative agreement between the experimental data and the calculations without any band renormalization, indicating strong

SOC effect but relatively weak electronic correlations in this material. In addition to the predicted bulk electronic bands, we observe two extra linearly dispersive bands marked with red dashed curves at several  $k_z$  planes, as shown in Figs. 2(b)–2(f). While the first one is fully occupied and locates at 1 eV below  $E_F$ , the second one is crossing  $E_F$  whereas it merges with the LDA predicted bulk band at  $k_z = \pi$  at low binding energy. By comparing the extracted dispersions at different  $k_z$ , we find that, although the bulk band structure has strong three-dimensional character, the Dirac cone-like bands are non-dispersive along  $k_z$ , thus suggesting that the extra bands are likely surface state bands (SSBs).

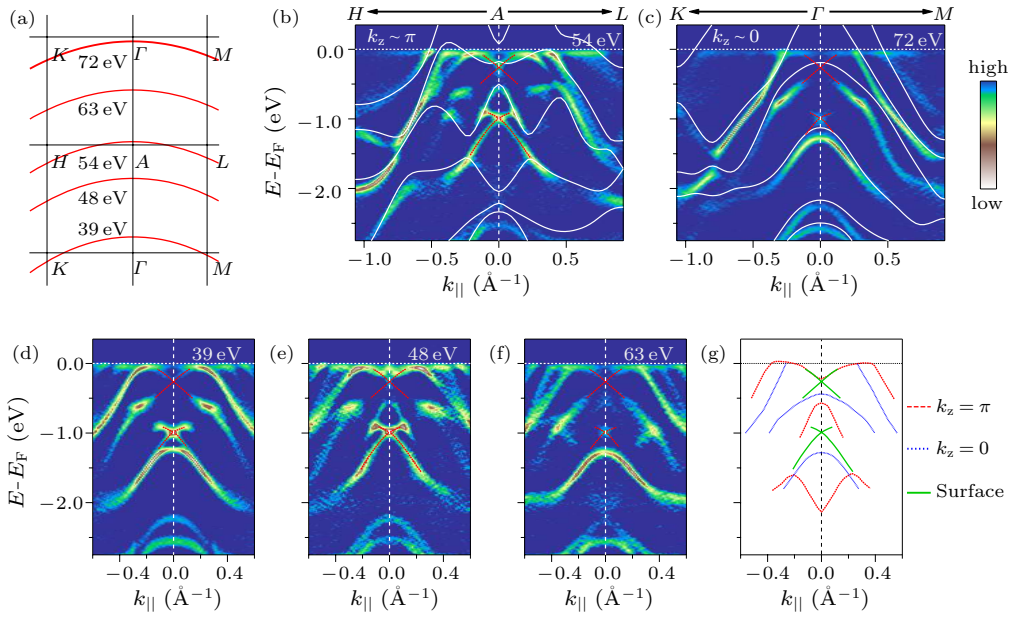

**Fig. 2.** (Color online) (a) Locations of photon energy dependent ARPES cuts in the momentum space. (b)–(f) ARPES curvature plots<sup>[22]</sup> of IrTe<sub>2</sub> at different photon energies. Red dashed curves represent the extra SSBs. White solid curves in panels (b) and (c) represent the LDA+SOC band structures at  $k_z = \pi$  and 0, respectively. (g) Extracted bulk bands at  $k_z = \pi$  and 0 and SSBs.


To further justify this claim, we performed *ab initio* calculations of the surface states on the (001) surface of IrTe<sub>2</sub>. We first construct the well-agreed maximally localized Wannier functions (MLWF)<sup>[23,24]</sup> from density function theory (DFT) calculations. We then use an iterative method<sup>[25,26]</sup> with these bulk MLWF hopping parameters to obtain the surface Greens function of the semi-infinite system. The imaginary part of the surface Greens function is the spectral function, from which we obtain the dispersion of the surface states, as shown in Fig. 3(b). In good agreement with the ARPES data, our calculations reveal two linearly dispersive SSBs.

In materials with strong SOC-like Bi<sub>2</sub>Se<sub>3</sub>, the linearly dispersive SSBs are topologically non-trivial and thus robust against non-magnetic impurities and weak crystal distortion. Since IrTe<sub>2</sub> also has a large SOC,

it is important to check whether the experimentally observed SSBs are topologically non-trivial. Figure 3(a) shows the main orbital components and parities of the low energy bulk bands at time-reversal invariant points. To determine the topological properties, we use the green and orange curves to represent the fictitious Fermi level curves, where the SSBs are identified. Unfortunately, the calculated topological Z<sub>2</sub> numbers below both the fictitious Fermi level curves are zero, proving that the observed surface states are topologically trivial.

To understand the origin of the SSBs, we analyze the dispersions and orbital components along the  $\Gamma$ - $A$  line. As seen in Fig. 3(a), the slide-down  $p_z \langle - \rangle$  band and the climb-up  $p_z \langle + \rangle$  band have a band-change and open two hybridization gaps along  $\Gamma$ - $A$ . This leads to two explicit Dirac cones at the projected point shown


in Fig. 3(b), corresponding to the fully occupied and the near- $E_F$  SSBs, respectively. As the parity analysis proves that the SSBs at the  $\Gamma$  point are topological trivial, one would expect Dirac cone-like SSBs at the M point. Such SSBs indeed exist at 1.6 and 2.2 eV below  $E_F$  at the projected M point according to our calculations as shown in Fig. 3(b), which are located at the fictitious Fermi level curves represented by the green and orange curves in Fig. 3(a), respectively, confirming that the experimentally observed SSBs are topologically trivial.

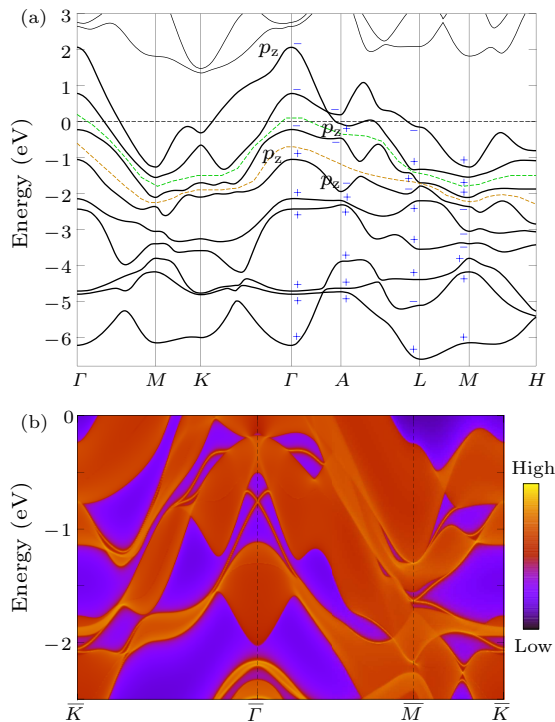

**Fig. 3.** (Color online). (a) Bulk band structure of IrTe<sub>2</sub> with SOC, in which the main components and parities of the low energy bands at time-reversal invariant points are listed. The green and orange curves are the fictitious Fermi level curves used to determine the topological properties of the system. (b) Calculated spectral function illustrating the band dispersion on the (001) surface. Two linear topological surface states are obtained, in agreement with the experimental observations.

Finally, we study the evolution of the SSBs in the SC (Pt<sub>x</sub>Ir<sub>1-x</sub>)Te<sub>2</sub>. The room temperature ARPES intensity plots, curvature plots and EDCs at  $k_z \sim 0$  and  $\pi$  are shown in Figs. 4(a)–4(c) and Figs. 4(d)–4(f), respectively. As compared with pristine IrTe<sub>2</sub>, both the bulk electronic bands and the SSBs of SC Pt<sub>0.05</sub>Ir<sub>0.95</sub>Te<sub>2</sub> barely change, proving that the parity analysis for IrTe<sub>2</sub> is still valid and thus that the Dirac cone SSBs observed in SC Pt<sub>0.05</sub>Ir<sub>0.95</sub>Te<sub>2</sub> are also topologically trivial. Moreover, by studying the electronic structure at low temperature, as shown in Figs. 4(g)–4(i), we find that the fully occupied SSB is shifted to higher binding energy and the near- $E_F$  SSB is almost completely smeared out while the bulk states remain unchanged. The change of these SSBs

at low temperature is consistent with the STM studies, where a complicated surface reconstruction at low temperature is observed in the SC Pt<sub>0.05</sub>Ir<sub>0.95</sub>Te<sub>2</sub>.<sup>[27]</sup>

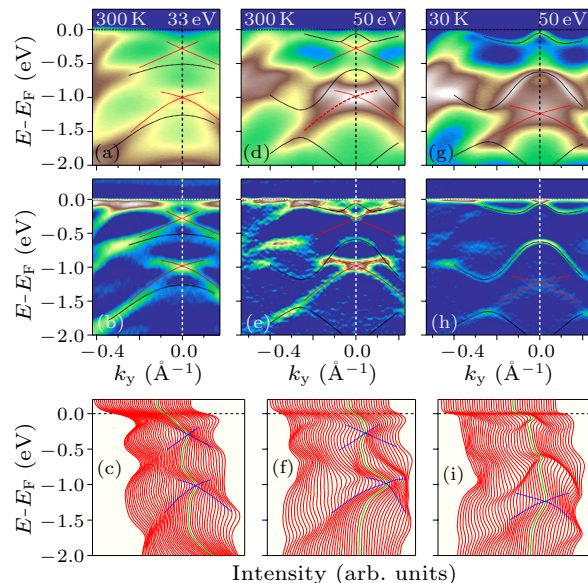

**Fig. 4.** (Color online) (a)–(c) Room temperature ARPES intensity plot and EDCs of (Pt<sub>x</sub>Ir<sub>1-x</sub>)Te<sub>2</sub> at  $k_z \sim 0$ . Red and black dashed curves represent the SSBs and bulk dispersions, respectively. Here (d)–(f) are the same as panels (a)–(c) while taken at  $k_z \sim \Gamma$ . (g)–(i) Low temperature ARPES intensity plot, curvature plot and EDCs at  $k_z \sim \Gamma$ .

In summary, we have resolved two Dirac cone-like SSBs in both non-SC IrTe<sub>2</sub> and SC Pt<sub>0.05</sub>Ir<sub>0.95</sub>Te<sub>2</sub>. Combined with the LDA calculations and parity analysis, we find that the experimentally observed SSBs are topological trivial. Although our results exclude SC (Pt<sub>x</sub>Ir<sub>1-x</sub>)Te<sub>2</sub> itself as a possible TSC candidate, recent STM and transport studies prove that (Pt<sub>x</sub>Ir<sub>1-x</sub>)Te<sub>2</sub> is a fully gapped s-wave superconductor with large  $c$ -axis coherence.<sup>[21]</sup> By utilizing the proximity effect, the heterostructure of TIs/(Pt<sub>x</sub>Ir<sub>1-x</sub>)Te<sub>2</sub> could be an ideal system to study the novel topological superconductivity.

We thank Wang Y. Y. for useful discussions. This work was based in part on research conducted at the Synchrotron Radiation Center, which is primarily funded by the University of Wisconsin-Madison with the University of Wisconsin-Milwaukee.

## References

- [1] Hasan M Z and Kane C L 2010 *Rev. Mod. Phys.* **82** 3045
- [2] Qi X L and Zhang S C 2011 *Rev. Mod. Phys.* **83** 1057
- [3] Fu L and Kane C L 2008 *Phys. Rev. Lett.* **100** 096407
- [4] Brouwer P W 2012 *Science* **336** 989
- [5] Fu L and Berg E 2010 *Phys. Rev. Lett.* **105** 097001
- [6] Sasaki S et al 2012 *Phys. Rev. Lett.* **109** 217004
- [7] Hor Y S et al 2010 *Phys. Rev. Lett.* **104** 057001
- [8] Wray L A et al 2010 *Nat. Phys.* **6** 855
- [9] Tanaka Y et al 2012 *Phys. Rev. B* **85** 125111
- [10] Kriener M et al 2011 *Phys. Rev. Lett.* **106** 127004

- [11] Zabolotnyy V B et al 2012 *New J. Phys.* **14** 063039
- [12] Liu S Y et al 2012 *Phys. Rev. B* **86** 165112
- [13] Nelson K D et al 2004 *Science* **306** 1151
- [14] Luke G M et al 1998 *Nature* **394** 558
- [15] Sato T, Tanaka Y, Nakayama K, Souma S, Takahashi T, Sasaki S, Ren Z, Taskin A A, Segawa K and Ando Y 2013 *Phys. Rev. Lett.* **110** 206804
- [16] Wang H, Wang H C, Liu H W, Lu H, Yang W H, Jia S, Liu X J, Xie X C, Wei J and Wang J 2015 arXiv:1501.00418[cond-mat.supr-con]
- [17] Yang J J, Choi Y J, Oh Y S, Horibe A, Kim K, Min B I and Cheong S W 2012 *Phys. Rev. Lett.* **108** 116402
- [18] Fang A F, Xu G, Dong T, Zhang P and Wang N L 2013 *Sci. Rep.* **3** 1153
- [19] Kiswandhi A, Brooks J S, Cao H B, Yan J Q, Mandrus D, Jiang Z and Zhou H D 2013 *Phys. Rev. B* **87** 121107(R)
- [20] Ootsuki D, Wakisaka Y, Pyon S, Kudo K, Nohara M, Arita M, Anzai H, Namatame H, Taniguchi M, Saini N L and Mizokawa T 2012 *Phys. Rev. B* **86** 014519
- [21] Yu D J, Yang F, Miao L, Han C Q, Yao M Y, Zhu F, Song Y R, Zhang K F, Ge J F, Yao X, Zou Z Q, Li Z J, Gao B F, Liu C, Guan D D, Gao C L, Qian D and Jia J F 2014 *Phys. Rev. B* **89** 100501
- [22] Zhang P, Richard P, Qian T, Xu Y M, Dai X and Ding H 2011 *Rev. Sci. Instrum.* **82** 043712
- [23] Marzari N and Vanderbilt D 1997 *Phys. Rev. B* **56** 12847
- [24] Souza I, Marzari N and Vanderbilt D 2001 *Phys. Rev. B* **65** 035109
- [25] Sancho M P L, Sancho J M L and Rubio J 1984 *J. Phys. F* **14** 1205
- [26] Sancho M P L, Sancho J M L, Sancho J M L and Rubio J 1985 *J. Phys. F* **15** 1581
- [27] Zhou X D and Wang Y Y *Private communication*